BACK TO BASICS...

Design and Selection of Hobs

Robert P. Phillips Barber-Colman Co. Specialty Tools Division Rockford, IL

Introduction

The following is a general overview of some of the different factors that lead to the specific design and the selection of the correct tool for a given hobbing application. There will be three main sections investigated:

- A. Basic review of the generating process as it relates to gear hobbing, including general nomenclature of hob terms, and specific tooth modifications.
- B. Hob error as it relates to gear accuracy.
- C. Optimization of hob design.

Hob Nomenclature

The terms in Fig. 1, along with additional terms and their definitions follow.

Nomenclature of Hob Elements and Other Terms Relating to Hobbing

- adjacent flute spacing The variation from the desired angle between adjacent tooth faces measured in the plane of rotation.
- adjacent thread spacing The difference in the average variations obtained by traversing along the desired helical path of one thread, indexing and traversing in a similar manner on an adjacent thread.

approach - See preferred term tip relief modification.

- approach distance The linear distance in the direction of feed between the point of initial hob contact and the point of full hob contact.
- arbor collar A hollow cylinder which fits an arbor, and is used to position the hob.

auxiliary leads - A feature employed on some hobs, especially

AUTHOR:

MR. ROBERT PHILLIPS is an Engineering Supervisor at the Barber-Colman Company where he supervises the design engineering of their hob product line. He holds a BS in Mechanical Engineering from the University of Wisconsin in Madison. He is a Certified Professional Engineer and has served as a SME Chapter Committeeman. worm gear hobs, wherein both sides of the hob thread have leads different from the nominal hob lead; one side longer, the other side shorter. This results in the tooth thickness being successively less toward the roughing end of the hob.

- axial feed The rate of change of hob position parallel to the workpiece axis usually specified in inches per revolution of the workpiece.
- axial plane A plane containing the axis of rotation.
- axial pressure angle See definition under pressure angle. back-off – See preferred term cam relief, under relief.
- cam The radial drop of the form in the angular distance between adjacent tooth faces.
- centering device A ground locating pin used to center a tooth or space of the hob on the centerline of the workpiece.
- chamfer A beveled surface to eliminate an otherwise sharp corner.
- climb hobbing Rotation of a hob in the opposite direction to the feed of the hob relative to the workpiece at the point of contact.

clutch keyway-See term keyway.

- common factor ratio In multiple thread hobs, the condition wherein the gear tooth-hob thread ratio is not a whole number, but there is a common factor of the number of gear teeth and the number of hob threads.
- conventional hobbing Rotation of a hob in the same direction as the feed of the hob relative to the workpiece at the point of contact.
- cutting face width The axial length of the relieved portion of the hob.
- cutting speed The peripheral lineal speed resulting from rotation, usually expressed as surface feet per minute. [sfm]
- depth of cut The radial depth to which the hob is sunk into the workpiece.
- drawbar A rod which retains the arbor, adapter or hob shank in the spindle.
- even ratio In multiple thread hobs, the condition wherein the gear tooth-hob thread ratio is a whole number.

feed - The rate of change of hob position while cutting.

fillet – 1 – A curved line joining two lines to eliminate a sharp internal corner. – 2 – A curved surface joining two surfaces

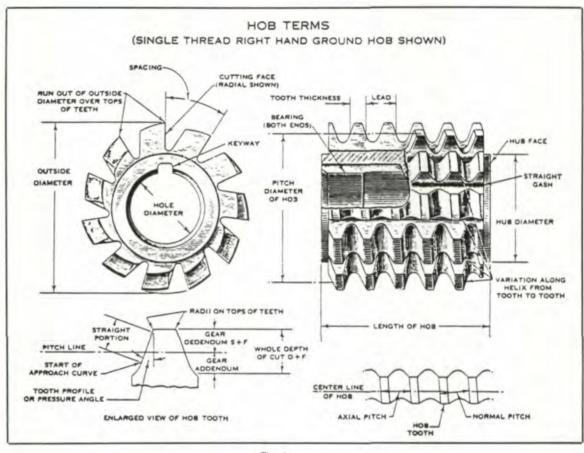


Fig. 1

to eliminate a sharp internal corner.

- flute A longitudinal groove either straight or helical that forms the tooth face of one row of hob teeth and the backs of the preceeding row. It also provides chip space.
- flute helix angle The angle which a helical tooth face makes with an axial plane, measured on the hob pitch cylinder.
- flute lead The axial advance of helical tooth face in one turn around the axis of a hob.
- flute lead variation The deviation of a hob tooth face from the desired helical surface.
- former-See preferred term sharpening guide.
- full top radius Continuous radius tangent to top and side cutting edges.
- gear tooth-hob thread ratio The ratio of the number of teeth in the workpiece to the number of threads in the hob.
- generated fillet At the bottom of the hobbed form a fillet joining the root diameter with the desired generated form. This fillet is not a true radius.
- generated fillet height On the hobbed workpiece, the radial distance from the root diameter to the point where the generated fillet joins the desired generated form.
- grinding cracks Fractures in the hob caused by improper grinding techniques in sharpening.

high point-See preferred term protuberance.

- hob addendum Radial distance between the top of the hob tooth and the pitch cylinder. Do not confuse with gear addendum.
- hob arbor A device to mount in or on the spindle of a hobbing machine, which is designed to carry and drive an arbor-type hob.
- hob dedendum In topping hobs, the radial distance between the bottom of the hob tooth profile and the pitch cylinder. Do not confuse with gear dedendum.

hob length - Overall length of hob.

- hob runout The runout of hob when mounted in hobbing machine, measured radially on hub diameter, and axially on hub face.
- hob shift The axial movement of a hob along its axis to engage a different section with the workpiece.
- hub A qualifying surface at each end of an arbor type hob which is provided for checking diameter and face runout.
- hub diameter runout The total variation in radial distance of the hub periphery from the axis.
- hub face The side surface of the hub.
- hub face runout The total axial variation of the hub face from a true plane of rotation.

hunting ratio-See preferred term prime ratio.

- infeed The radial rate of change of hob position, relative to the workpiece axis, usually specified in inches per revolution of the workpiece.
- key A mechanical member through which the turning force is transmitted to the hob.
- keyseat The pocket, usually in the driving element, in which the key is retained.
- keyway A slot through which the turning force is transmitted to the hob. May be either a longitudinal slot through the hole or a transverse slot across the hub face. If the latter, it is called a clutch keyway.
- lead The axial advance of a thread for one complete turn, or convolution.
- lead angle The angle between any helix and a plane of rotation. In a hob, lead angle usually refers specifically to the angle of thread helix measured on the pitch cylinder.
- lead variation The axial deviation of the hob teeth from the correct thread lead.
- leader-See preferred term sharpening guide.
- linear pitch See preferred term axial pitch, under pitch.
- linear pressure angle See preferred term axial pressure angle, under pressure angle.
- lug An extension of hob tooth profile above the nominal top cutting edge. Sometimes called spurs or prongs.
- non-adjacent flute spacing The variation from the desired angle between any two non-adjacent tooth faces measured in the plane of rotation.
- normal circular pitch-See definition under pitch.
- normal diametral pitch-See definition under pitch.
- normal plane A plane perpendicular to a pitch cylinder helix.

normal pressure angle - See definition under pressure angle.

number of threads – In multiple thread hobs, the number of parallel helical paths along which hob teeth are arranged, sometimes referred to as number of starts. Should not be confused with the term, number of threads per inch, which is commonly used in designating the axial pitch of screw threads.

offset - See preferred term rake offset.

- outside diameter The diameter of the cylinder which contains the tops of the cutting edges of the hob teeth.
- outside diameter runout The total variation in the radial distance from the axis to the tops of the hob teeth.
- overtravel The linear distance in the direction of feed of the hob beyond the last point of contact of the hob with the workpiece.
- pilot end On shank type hobs, a cylindrical or conical bearing surface opposite the driving end.
- pin measurement The measurement taken over pins of equal diameter placed in specified tooth spaces in the workpiece.
- pitch The distance between corresponding, equally spaced hob thread elements along a given line or curve. The use of the single word pitch without qualification may be confusing. Specific terms such as normal diametral pitch, normal circular pitch, or axial pitch are preferred.
 - Axial Pitch The pitch parallel to the axis in an axial plane between corresponding elements of adjacent hob thread sections. The term Axial Pitch is preferred to the term Linear Pitch.

Circular Pitch – The distance along the pitch cylinder between corresponding elements of adjacent hob thread sections.

Linear Pitch-See preferred term Axial Pitch.

- Normal Circular Pitch The distance between corresponding elements on adjacent hob thread sections measured along a helix that is normal to the *Thread Helix* in the *Pitch Cylinder*.
- *Normal Diametral Pitch* π [3.1416] divided by the *Normal Circular Pitch*.

pitch circle - A transverse section of the hob pitch cylinder.

- pitch cylinder A reference cylinder in a hob from which design elements, such as lead, lead angle, profile, and tooth thickness are derived.
- pitch diameter The diameter of the pitch cylinder.
- pitch point The point at which a tooth profile intersects the pitch cylinder.
- pressure angle The angle between a tooth profile and a line perpendicular to the pitch cylinder at the pitch point. In hobs, the pressure angle is usually specified in the normal plane or in the axial plane.
 - Axial Pressure Angle The Pressure Angle as measured in an Axial Plane. The term Axial Pressure Angle is preferred to the term Linear Pressure Angle.
- Normal Pressure Angle The Pressure Angle as measured in a Normal Plane.
- prime ratio In multiple thread hobs, the condition wherein the gear tooth-hob thread ratio is not a whole number and there is no common factor of the number of gear teeth and the number of hob threads.
- protuberance A modification near the top of the hob tooth which produces undercut at the bottom of the tooth of the workpiece.
- rake The angular relationship between the tooth face and a radial line intersecting the tooth face at the hob outside diameter measured in a plane perpendicular to the axis. *Negative Rake* – The condition wherein the peripheral cut
 - ting edge lags the tooth face in rotation.
 - Positive Rake The condition wherein the peripheral cutting edge leads the tooth face in rotation.
 - Zero Rake-The condition wherein the tooth face coincides with a radial line.
- rake offset The distance between the tooth face and a radial line parallel to the tooth face. Used for checking rake.
- ramp A modification at the bottom of the hob tooth which produces a chamfer at the top corners of the tooth of the workpiece.
- relief The result of the removal of tool material behind or adjacent to a cutting edge provide clearance and prevent rubbing [heel drag].
 - Cam Relief The relief from the cutting edges to the back of the tooth produced by a cam actuated cutting tool or grinding wheel on a relieving [back-off] machine.
 - Side Relief The relief provided at the sides of the teeth behind the cutting edges. The amount depends upon the radial cam, the axial cam, and the nature of the tooth profile.
- scallops The shallow depression on the generated form produced by hob action.

setting angle - The angle used for setting hob swivel to align

the hob thread with the workpiece teeth.

- shank That projecting portion of a hob which locates and drives the hob in the machine spindle or adapter.
- sharpening allowance The amount by which the pitch diameter of a worm gear hob exceeds that of the worm, to allow for the reduction in diameter by sharpening.
- sharpening guide A cylindrical part with flutes, having the same lead as the hob flutes, used for guiding the hob along the correct lead when sharpening.
- short lead A feature employed on some hobs to obtain generated fillet or undercut conditions not obtainable with nominal lead.
- side relief-See definition under relief.
- stock allowance The modification of the hob tooth to leave material on the workpiece tooth form for subsequent finishing.
- tangential feed The rate of change of hob position along its own axis, usually specified in inches per revolution of the workpiece.
- thread A helical ridge, generally of constant form or profile. In a hob, unlike a worm or screw, the thread is not continuous and exists only at the cutting edges of the hob teeth. Therefore, it is sometimes referred to as the thread envelope.

thread envelope - See preferred term thread.


- thread helix The helix of the hob thread in the pitch cylinder.
- tip relief A modification in which a small amount of material is removed from the basic profile near the tip of the gear tooth.
- tip relief modification A modification on the sides of the hob tooth near the bottom which produces a small amount of tip relief. Such modification is usually incorporated in finishing hobs except in the finer pitches.

tooth – A projection on a hob which carries a cutting edge. tooth face – The tooth surface against which the chips impinge.

tooth profile - Outline or contour of hob tooth cutting edges.

- tooth thickness The actual width or thickness of the hob thread at the pitch cylinder. The use of the single term tooth thickness without qualification may be confusing. The specific terms normal tooth thickness and axial tooth thickness are preferred.
 - Axial Tooth Thickness The tooth thickness as measured in an axial plane.
 - Normal Tooth Thickness The tooth thickness as measured along a helix normal to the thread helix.
- top radius Radius of the arc joining the top and a side cutting edge of a hob tooth.
- total indicator reading [tir] See preferred term total indicator variation.
- total indicator variation [tiv] The difference between maximum and minimum indicator readings during a checking cycle.
- undercut The condition at the base of a hobbed workpiece form wherein additional material beyond the basic form is removed. Under certain conditions this may occur naturally, while in other cases it may be produced by intentional modification of the hob tooth.

wear land - A cylindrical or flat land worn on the relieved

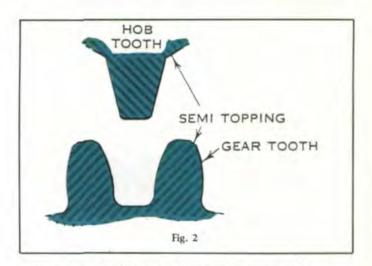

portion of the hob tooth behind the cutting edge.


- wobble The motion of a hob when the radial runout varies along the hob length.
- worm gear hob oversize See preferred term sharpening allowance.

For varying specific reasons, it is possible to alter the straight sided rack form in order to achieve a modified generated gear tooth form.

The hob in Fig. 2 was designed to eliminate sharp corners at the tops of gear teeth. It can be made to produce a desired amount of chamfer or radius, but to do this the number of teeth in the gear must be known. Obviously, the form of such a modification produced by a given hob will vary with the number of teeth in the gear, just as the width of the top of the gear tooth varies.

The topping gear hob shown in Fig. 3 is used for cutting spur gears and helical gears. This hob finishes the tops of gear teeth, holding the outside diameter of the gear to a given dimension in relation to the pitch line and root diameter.

Several advantages accompany the use of topping hobs that in many cases result in material savings. For instance, the finish-hobbed gears may be chucked on the outside diameter in subsequent operations for hole finishing when necessary. Moreover, their use eliminates an accurate finish-turning operation on gear blanks before hobbing. Additionally, gears hobbed with topping hobs may be quickly inspected for pitch line thickness to ordinary commercial limits by measuring the outside diameter with a micrometer.

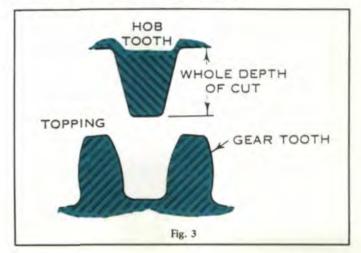

Portable, versatile, simplified hardness testing with high repeatability



Ultrasonic Hardness Tester

Expand your quality-control procedures: Check hardness in tight places, e.g. flanks of small gear teeth. Test parts as thin as .003" (sheet, tubing, plating, case-hardened surfaces). Read HRC 20.0-68.0 and HV 050-990 directly on digital LED display. Use for on-site inspection anywhere (less than 4 pounds with battery and probe).

MICRODUR advantages: Virtually nondestructive (indentation depth is only 5 to 23 microns) • Standard interchangeable probe heads available for curved and flat magnetic surfaces and for hard-to-reach parts • One-point calibration for easy use • Semi-automatic—motorized probe reduces operator influence, enhances repeatability.

For details, call or write: Krautkramer Branson, Inc., P.O. Box 350, Lewistown, PA 17044; (717) 242-0327 or (717) 242-0331.



Krautkramer Branson

©Krautkramer Branson Incorporated 1985

CIRCLE A-12 ON READER REPLY CARD

Gears are frequently hobbed and then finished by shaving or grinding. Hobs for producing such gears are referred to as semi-finishing hobs. The hobbing of such gears has not been considered a roughing operation because of the accuracy required for leaving a minimum and uniform amount of finishing stock. (Fig. 4)


The protuberance type hob shown in Fig. 5 generates undercut at the bottom of the gear tooth to provide clearance for the shaving cutter and to prevent the formation of an abrupt change in profile with its resulting stress concentration. With small numbers of teeth, the tooth form cut with a hob without protuberance is often undercut enough, but a protuberance is required for larger numbers of teeth to eliminate contact between the tip of the shaving cutter and the fillet on the gear tooth.


Hob Error vs. Gear Accuracy

All hob manufacturers work to a given set of standard tolerances. A reprint of tolerances from the Metal Cutting Tool Institute Standards are as follows. It should be noted, these tolerances pertain to standard outside diameter sizes only. (Table of standard hob sizes – see pages 40-43) Tolerances for lead on oversized hobs can be increased proportionally to the diameter increase.

Tolerance Definitions Hole

diameter – The basic diameter of the hole in the hob.
tolerance – The amount that a hole may be oversize from the basic diameter of the hole.

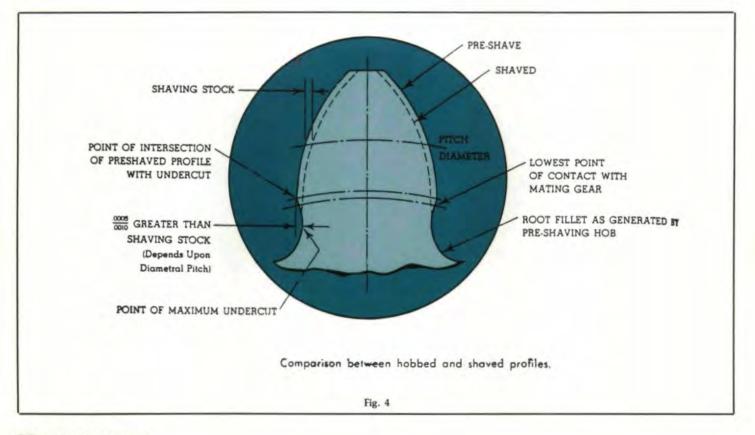

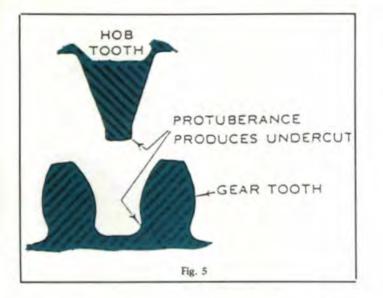

bearing contact – The area of contact obtained using a plug gage that makes contact over the full length of the hob.

Runout

- hub face The total indicator variation on the end face in one revolution of the hob.
- hub diameter-The total indicator variation on the hub diameter in one revolution of the hob.
- outside diameter The total indicator variation on the tops of the hob teeth in one revolution of the hob.

Sharpening


- spacing between adjacent flutes The total indicator variation obtained between two successive flutes when a hob is indexed.
- spacing between non-adjacent flutes The total indicator variation obtained between any two flutes when the hob is indexed through one complete revolution.
- rake to cutting depth The total indicator variation when traversing the tooth face from the top to the cutting depth.
- flute lead The total indicator variation when traversing the faces of all of the teeth in any one flute following the specified lead.

Lead Variation

- tooth-to-tooth The total indicator variation on successive teeth when traversing along the true helical path.
- any one axial pitch The total indicator variation in one complete revolution along the true helical path (360 degrees) on a single thread hob.
- any three axial pitches The total indicator variation in three revolutions along the true helical path (1080 degrees) on a single thread hob.
- total The total indicator variation on teeth when traversing along true helical path of all teeth in hob.

Tooth Profile

pressure angle or profile – The departure of the actual tooth profile from the correct tooth profile as denoted by total indicator variation or by magnified layout comparison.

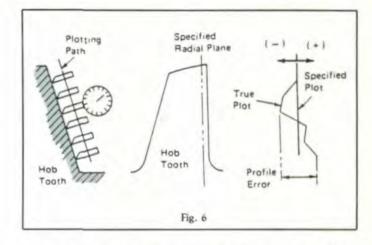


Tolerances shown apply to straight side profiles in the axial or normal section.

Hobs with curved profiles are special and subject to individual consideration.

- tooth thickness The difference between the measured thickness and the specified thickness at the hob pitch cylinder.
- start of tip relief modification The tolerance permitted in locating the point on the hob tooth, plus or minus, at which a profile modification begins.
- symmetry in start of tip relief modification The radial tolerance for the start of the modification with reference to the start of the modification on the opposite hob tooth profile.

Hob profile error

The actual hob profile is allowed to vary from the specified hob profile entirely in the plus direction, entirely in the minus direction or split and divided in any ratio, provided the total deviation does not exceed the specified value. This maximum value can occur anywhere along the hob profile, and the variation of the profile on one side of the thread has no relationship to the variation on the other side of that same thread. (See Fig. 6)

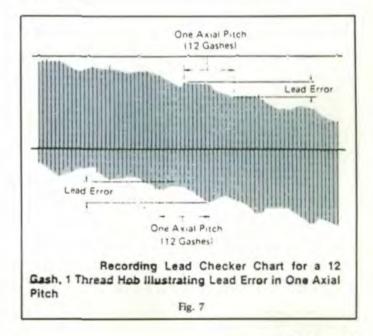

SINGLE-THREAD AND MULTITHREAD GEAR HOB TOLERANCES

(All readings in tenths of a thousandth of an inch)

DIAMETRAL PITCH		1 Thru 1.999	2 Thru 2.999	3 Thru 3.999	4 Thru 4.999	5 Thru 5.999	6 Thru 8.999	9 Thru 12.999	13 Thru 19,999	20 Thru 29.999	30 Thru 50.999	51 and Fine
RUNOUT (1.4 Thread)	CLASS								_			
	AA			2	2	2	1	1	1	1	1	1
Ilub Face*	A	8	5	2	2	2	2	2	2	2	2	2
	В	10	8	4	4	3	3	2	2	2	2	
	C	10	8	.4	4	3	3	2	2	2	2	2
	D	10	8	5	5	4	4	3	3	3	3	
	AA			2	2	2	1	1	1	1	1	1
Hub Diameter*	A	10	5	4	3	3	3	2	2	2	2	2
indir Diministr	B	12	8	6	5	.1	4	3	2	2	2	
	C	12	8	6	5	4	4	3	2	2	2	2
	D	15	10	8	8	6	6	5	5	4	3	-
	AA	10	10	5	4	3	3	3	3	2	2	2
Outside Diameter*	A	30	20	15	15	10	10	10	10	10	7	5
Outside Mameter	B	10	30	25	20	15	15	15	10	10	7	3
									1.1			
	C	50	45	-40)	25	20	17 35	17 30	12 25	12 20	10 15	8
	D	60	55	50	45	35	35	30	20	20	15	
EAD VARIATION												
	AA	20	1725	+	3	2	1.7	1.7	1.7	1.7	1.5	1.3
Tooth to Tooth*	A	7	5	4	3	2	2	2	2	2	2	2
1 Thread	B	10	8	6	4	3	3	3	3	3	2	
	C	15	12	8	6	5	4	4	4	4	3	3
	D	25	20	16	14	12	10	10	8	6	5	-
SIZ WAR	A	8	6	5	4	3	3	3	3	2	2	2
2 Thread	В	12	10	7	6	5	5	5	4	3	2	
	С	18	14	10	9	7	6	6	5	5	3	3
	D	27	22	18	16	14	12	11	9	8	6	
	A	9	7	6	-4	4	4	3	3	3	2	2
3 Thread	В	14	12	8	7	6	6	5	5	4	3	-
· · · · · · · · · · · · · · · · · · ·	C	21	16	12	10	8	7	6	5	5	4	3
	D	29	24	20	18	16	14	12	10	9	7	
	A	10	7	6	5	4	4	4	3	3	3	2
4 Thread	B	16	13	9	8	7	6	6	5	4	4	-
F THICAN	C	24	18	13	11	9	7	7	6	5	4	4
	D	31	26	22	20	18	16	13	11	10	8	
		01	20	8	6	4	3	3	2			1.
Any One Axial Pitch*	AA A	25	18	10	8	6	5	5	4	2 4	1.5	3
						9	-					2
1 Thread	B C	35 45	25 35	17 22	11 14	11	7 9	7 9	6 8	6	4 8	
	D	45	35 50	40	30	25	20	20	18			6
										16	14	
0.470	Α	25	20	10	8	6	5	5	4	4	3	3
2-4 Thread	B	35	30	17	12	10	8	8	7	7	4	
	C	45	3.5	22	18	15	12	12	10	10	8	6
	D	60	50	40	30	25	20	20	18	16	14	-
a charles and a	AA			12	9	6	5	5	4	4	3	3
Any Three Axial Pitches*	A	38	26	15	12	9	8	8	7	7	5	5
1 Thread	B	53	38	22	16	12	11	10	9	9	7	
	С	70	50	30	21	16	14	13	12	12	12	8
	D	120	100	80	60	50	40	35	25	20	16	

*Total indicator variation. Class AA Ultra Precision Hobs are made single thread only. Tolerances apply only to standard or recommended hob diameters.

(All readings in tenths of a thousandth of an inch)

CLASS A B C D A B C D A B C D A B C D A B C D	1.999 38 53 70 120 11 14 20 26 13 16 22 28 15 18	2.999 30 38 50 100 9 12 17 22 11 14 19 24	15 22 30 80 8 11 15 19 10 12 16	12 20 28 60 7 10 13 17 8	5.999 9 15 20 50 6 9 11 15	8 12 18 -40 5 8 10 13	12.999 8 12 16 35 4 6 9	19.999 7 10 1.4 25 3 5 8	7 10 14 22 3 5 7	5 7 12 18 3 5 6	5 8 3 5
A B C D A B C D A B C D A B C D A B C C D	53 70 120 11 14 20 26 13 16 22 28 15	38 50 100 9 12 17 22 17 22 11 11 14 19 24	22 30 80 8 11 15 19 10 12	20 28 60 7 10 13 17 8	15 20 50 6 9 11 15	12 18 40 5 8 10	12 16 35 4 6 9	10 14 25 3 5 8	10 14 22 3 5	7 12 18 3 5	8
C D A B C D A B C D A B C D A B C C	70 120 11 14 20 26 13 16 22 28 15	50 100 9 12 17 22 11 14 19 24	22 30 80 8 11 15 19 10 12	20 28 60 7 10 13 17 8	20 50 6 9 11 15	18 -40 5 8 10	16 35 4 6 9	14 25 3 5 8	14 22 3 5	12 18 3 5	3
D A B C D A B C D A B C	120 11 14 20 26 13 16 22 28 15	100 9 12 17 22 11 14 19 24	30 80 8 11 15 19 10 12	60 7 10 13 17 8	20 50 6 9 11 15	18 -40 5 8 10	16 35 4 6 9	25 3 5 8	22 3 5	18 3 5	3
D A B C D A B C D A B C	120 11 14 20 26 13 16 22 28 15	9 12 17 22 11 14 19 24	8 11 15 19 10 12	60 7 10 13 17 8	50 6 9 11 15	40 5 8 10	35 4 6 9	3 5 8	22 3 5	18 3 5	
A B C D A B C D A B C	11 14 20 26 13 16 22 28 15	12 17 22 11 14 19 24	11 15 19 10 12	10 13 17 8	9 11 15	8 10	4 6 9	3 5 8	3 5	5	
B C D A B C D A B C	14 20 26 13 16 22 28 15	12 17 22 11 14 19 24	11 15 19 10 12	10 13 17 8	9 11 15	8 10	6 9	5 8	5	5	
C D A B C D A B C	20 26 13 16 22 28 15	17 22 11 14 19 24	15 19 10 12	13 17 8	11 15	10	9	8			5
D A B C D A B C	26 13 16 22 28 15	22 11 14 19 24	19 10 12	17	15						
A B C D A B C	13 16 22 28 15	11 14 19 24	10 12	8			12	11	10	9	
B C D A B C	16 22 28 15	14 19 24	12		-		5	_			3
C D A B C	22 28 15	19 24			7	6		4	+	4	2
D A B C	28 15	24		11	10	9	7	7	6	6	
A B C	15			14	13	11	10	9	8	7	6
B C			20	18	16	15	13	12	11	10	
С	10	13	12	9	8	7	6	5	4	4	3
		16	14	12	11	10	8	7	7	6	
-	24	21	18	15	14	12	11	10	9	8	7
D	30	26	22	20	18	16	14	13	12	11	
							_	-			
AA			2	2	1.7	1.7	1.7	1.7	1.7	1.5	1.5
	10	5									2
											3
			5					2		2	2
											~
											3
						-					0
									9		2
											4
											3
								-	-		2
	00	55								_	
		100									
				0.00							
-	260			200	180	160	140	120		80	
Α	200	180	160	140	120	100	80	60	50	4()	
В	220	200	180	160	140	120	100	80	60	50	
	220	200	180	160	140	120	100	80	60	50	
D	260	2.40	220	200	180	160	140	120	100	80	
AA			70	60	50	-40	40	25	25	25	
	150	130			90	80	60				
			130		100	90			45		
			160				100	90	80		
	AA A B C D A B C D A A B C D A A A B C D A A B C D A A A A A A B C D A A B C D A B C D A B C D A B C D A A B C D A A B C D A A A A A A B C D A A A A A A A A A A A A A A A A A A	AA 10 B 16 C 25 D 80 A 12 B 18 C 27 D 80 A 15 B 20 C 27 D 80 A 15 B 20 C 27 D 80 AA 15 B 200 C 220 D 260 A 200 B 220 C 220 D 260 AA 150 B 180 C 180 D 200 A 150 B 180 C 180 C 180 C 180 C 180 C 180	$\begin{array}{c ccccccccccccccccccccccccccccccccccc$	$\begin{array}{c ccccccccccccccccccccccccccccccccccc$	$\begin{array}{c ccccccccccccccccccccccccccccccccccc$	$\begin{array}{c ccccccccccccccccccccccccccccccccccc$	$\begin{array}{c c c c c c c c c c c c c c c c c c c $	$\begin{array}{c c c c c c c c c c c c c c c c c c c $	$\begin{array}{c c c c c c c c c c c c c c c c c c c $	$\begin{array}{c c c c c c c c c c c c c c c c c c c $	$\begin{array}{c c c c c c c c c c c c c c c c c c c $

*Total indicator variation. Class AA Ultra Precision Hobs are made single thread only. Tolerances apply only to standard or recommended hob diameters.

(All readings in tenths of a thousandth of an inch)

DIAMETRAL PITCH		1 Thru 1.999	2 Thru 2.999	3 Thru 3.999	4 Thru 4.999	5 Thru 5.999		9 Thru 12.999	13 Thru 19.999	20 Thru 29.999	30 Thru 50.999	51 and Finer
TOOTH PROFILE (con't.)	CLASS											
	AA			15	15	10	10	10	10	10	5	5
Tooth Thickness	Λ	30	20	15	15	10	10	10	10	10	5	5
(Minus Only)	B	30	20	15	15	10	10	10	10	10	5	
1-4 Thread	č	35	25	20	20	15	15	15	15	15	10	10
1-4 Inteau	D	40	35	30	25	20		20	20	20	15	10
SHARPENING (1 - 4 Thread)												
	AA			20	15	10	8	8	6	6	6	6
Spacing Between	A	40	30	25	20	15	10	10	10	10	10	10
Adjacent Flutes*	В	50	45	40	30	20		15	10	10	10	
	C	50	45	40	30	20		15	10	10	10	10
	D	60	60	50	50	30		25	20	17	17	
	AA			40	35	25		15	15	15	15	15
Spacing Between	A	80	60	50	* 40	30		30	25	25	20	20
Non-Adjacent Flutes*	B	100	90	80	60	50		50	40	35	30	
1101-Aujacene i luces	č	100	90	80	60	50		50	40	35	30	30
	D	120	120	100	100	80		70	60	50	40	50
	AA			10	8	6		5	3	3	3	3
Cutting Faces	A	30	15	10	8	6		5	3	3	3	3
Radial To	B	50	25	15	IU	8		7	5	5	5	Ŷ.
Cutting Depth*	č	50	25	15	10	8		7	5	5	5	5
Curring Deprin	D	100	75	50	40	30		20	15	15	10	3
		FACE W	IDTH		o 1"		o 2″	2" to 4		" to 7"		and up
	AA	-			8	1	0	15		20		20
Accuracy of Flutes,	A				10		5	25		30		50
Straight And Helical*	B				10		5	25		30		50
	C				10		5	25		30		50
	D				15		3	38		45		75
BORE (1-4 Thread)		-										
		E DIAM	ETER	2.500"	2.0	00″	1.500"	1.250	".7	50"	.500" &	smalle
and a start and a start of the	AA							2		2		2
Diameter, Straight Bore	Λ			8		8	5	2		2		2
(Plus Only)	В			10	1	0	8	3		2		2
	С			10	1	-	8	3		2		2
	D			10	1	0	8	5	_	4		3
		A	LL DI	AMETH	ERS		LENG	1. 1. 1. I.				
	AA						75					
Percent of Bearing	A						75					
Contact, Straight Borc	B C						75					
	C						60					
	D		-	_		-	50					
			ALL 1	FAPER	S	CIR	CUMF	ERENC	E	LI	ENGTH	I
Percent of Bearing	AA						95				75	
Contact, Taper Bore	A						90	-			60	
	В						90				60	
	C						90				60	

*Total indicator variation. Class AA Ultra Precision Hobs are made single thread only. Tolerances apply only to standard or recommended hob diameters.

STANDARD HOB SPECIFICATIONS & TOLERANCES RECOMMENDED HOB SIZES

Single Thread Coarse Pitch Hob Sizes for Ground and Unground Hobs

(1-19.99 Normal Diametral Pitch)


For Spur and Helical Gears

Normal Diametral Pitch	Nominal Hole Diameter	Outside Diameter	Overall Length
1	21/2"	103/4"	15"
11/4	2"	81/4"	12"
11/2	2"	8"	10"
13/4	2"	71/4"	9"
2.00-2.24	11/2"	51/4"	8"
2.25-2.49	11/2"	51/2"	71/2"
2.50-2.74	11/2"	5"	7"
2.75-2.99	11/2"	5"	6"
3.00-3.49	11/4"	41/2"	5"
3.50-3.99	11/4"	41/4"	43/4"
4.00-4.99	11/4"	4"	4"
5.00-6.99	11/4"	31/2"	31/2"
7.00-7.99	11/4"	31/4"	31/4"
8.00-11.99	11/4"	3″	3"
12.00-13.99	11/4"	23/4"	23/4"
	3/4"	2″	2"
14.00-19.99	11/4"	21/2"	21/2"
	3/4"	17/8"	17/8"

Single Thread Fine Pitch Hob Sizes for Ground and Unground Hobs

(20 Normal Diametral Pitch and Finer) For Spur and Helical Gears

Normal Diametral Pitch	Nominal Hole Diameter	Outside Diameter	Overall Length
20-21.99	1¼"	2½"	2½"
	¾"	1%"	17/8"
22-23.99	11/4"	2½"	2"
	3/4"	1%"	17/8"
24-29.99	11⁄4"	2½"	2"
	3⁄4"	1%"	17/8"
	1⁄2"	1¼"	1 ¹ /4"
30-55.99	^{3/4} "	17%"	1½"
	^{1/2} "	1%"	1½"
	.3937 (10 mm)	1%"	¾"
	.315 (8 mm)	7%"	½"
56-85.99	³ /4"	15%"	1 ¹ /8"
	1/2"	11/8"	1 ¹ /8"
	.3937 (10 mm)	11/8"	3/4"
	.315 (8 mm)	7/8"	1/2"
86-130.99	³ /4"	1½"	3/4"
	1/2"	1¼"	7/8"
	.3937 (10 mm)	1"	3/4"
	.315 (8 mm)	3/4"	1/2"
131-200	³ /4"	13/8"	5/8"
	1/2"	11/8"	1/2"
	.3937 (10 mm)	1"	1/2"
	.315 (8 mm)	3/4"	1/2"

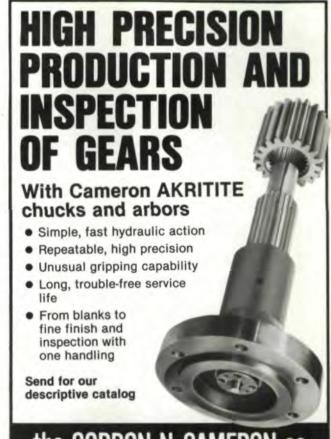

the GORDON N. CAMERON co.

859 E. Whitcomb Blvd. • Madison Heights, MI 48071 • Phone (313) 588-0215

Multiple Thread Course Pitch Hob Sizes for Ground and Unground Hobs (2-19.99 Normal Diametral Pitch) For Spur and Helical Gears					
Normal Diametral Pitch	Number of Threads	Nominal Hole Diameter	Outside Diameter	Overall Length	
2-2.99 3-3.99 4-4.99 5-6.99	2 2 2 or 3 2, 3 or 4	1½" 1½" 1½" 1½"	61/2" 51/2" 51/2" 51/2" 5"	8" 5½" 5½" 5"/2"	
7-7.99 8-8.99 9-11.99 12-13.99	2, 3 or 4 2, 3 or 4 2, 3 or 4 2, 3 or 4	1¼4" 1¼4" 1¼4" 1¼4"	4" 3 ³ /4" 3 ¹ /2" 3 ¹ /4"	4" 3¾" 3½" 3¼"	
14-15.99 16-19.99	2, 3 or 4 2, 3 or 4	1¼" 1¼"	3" 2¾"	3" 23/4"	

Multiple Thread Fine Pitch Hob Sizes for Ground and Unground Hobs (20 Normal Diametral Pitch and Finer)

For Spur and Helical Gears

	For Spi	ar and rielical	Gears	
Normal Diametral Pitch	Number of Threads	Nominal Hole Diameter	Outside Diameter	Overall Length
20-29.99	2, 3 or 4	11/4"	21/2"	21/2"


3/4"


2, 3 or 4

30-50

1%"

11/2"

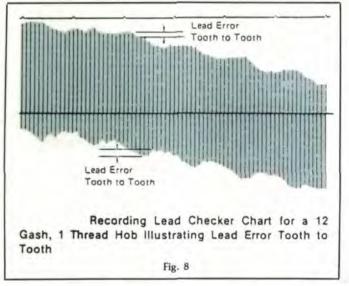

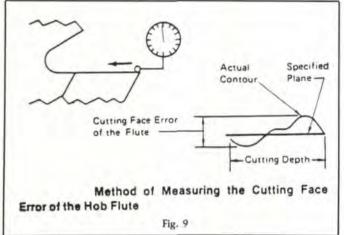

Lead error - one axial pitch


Lead error in one axial pitch is the maximum deviation from the theroretical thread helix in any group of hob teeth equal to the number of hob teeth in one axial pitch. This number of hob teeth may be selected anywhere in the length of the hob and is equal to the number of hob gashes divided by the number of hob threads. (See Fig. 7)

Lead error - tooth-to-tooth

Tooth-to-tooth lead error is the maximum deviation between any two consecutive hob teeth from their relative position as measured at any point along the thread in the entire hob length. Fig. 8 illustrates this error as read from an automatic lead checker chart.

Cutting face error

The cutting faces of the hob flute are usually designed to lie in a given radial plane in the case of straight flute hobs and in a specific helicoidal surface for helical flute hobs. However, in straight flute hobs the plane can be radial or can be inclined in either direction from radial providing either positive or negative rake. When the cutting faces are designed to lie in a plane, the variation of the actual hob flute cutting faces from that plane is considered to be a flute cutting face

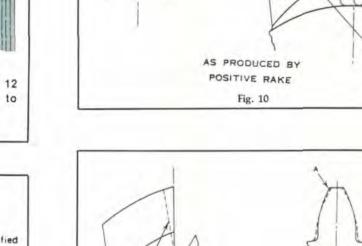

AS PRODUCED BY NEGATIVE RAKE Fig. 11

error. (See Fig. 9)

Positive rake in sharpening increases depth and decreases pressure angle of the hob tooth. The resulting gear tooth is too heavy at the top and too thin at the bottom as shown in Fig. 10.

Negative rake in sharpening decreases the depth and increases the pressure angle of the hob tooth. This results in a cutting drag and makes the gear tooth lighter at the top and heavier at the bottom. (See Fig. 11)

Optimizing Tool Design

Multiple thread hobs

The two primary considerations in determining the number of threads on the hob are the production requirements and the accuracy and finish requirements. Increased production is the outstanding advantage of multithread hobs.

A single-thread hob rotates once for each tooth on the part, a double-thread hob rotates once for every two teeth on the part, a triple-thread hob rotates once for every three teeth, etc. Therefore, the workpiece rotates faster in relation to the hob speed, depending upon the number of threads on the hob.

The increase in the speed of indexing, however, does not usually result in a proportional gain in production. The diameter of a multithread hob is larger than a corresponding single-thread hob but does not increase in proportion to the number of threads. Therefore, the number of flutes does not increase in direct proportion to the number of threads.

Material

When considering the total manufacturing cost per metal cutting operation the price of the tool is, in fact, minor in percentage. It is not uncommon that the purchase cost of a tool will amount to only about 5% of the total cost per part. With this in mind, it follows that simply buying the cheapest tool is not an effective way of reducing cost.

If the purchase price of the tool is combined with the cost of resharpening the tool, we find that the total tool cost is approximately 15% of the metal cutting cost per part produced. The balance, or about 85%, is considered machining cost. This will be discussed in detail later. The percentage stated above are for gear cutting tools such as hobs and shaper cutters. Less expensive tools will have different ratios. Table 1 shows the relative cost of tools made of different steels as they are related to the base price of an M2 tool.

Table 1 takes into account both the increase due to material cost (premium steels because of manufacturing process and alloying elements generally are more expensive) and the additional machining cost encountered by the tool manufacturer.

The life of any particular tool is directly related to the following factors:

- a. Crater wear
- b. Corner/flank wear
- c. Chipping

Crater wear is largely a function of red hardness and abrasion resistance of the tool steels being examined. The usual causes of cratering are cutting conditions (speed and feed) too high for the tool material.

Corner/flank wear depends on micro-chipping due to lack of toughness or abrasive wear due to lack of hardness. Under normal conditions, it is flank wear that puts the limit on the life of the tool.

Chipping occurs when the tensile strength of particular tool steel is exceeded. This type of wear is due to brittle tool materials subjected to excessive mechanical loads.

		TABLE	L,	
M2	M2HC	M3	M4	M35
100	100	125	2125	140
M42	REX 20	REX 25	REX 76	T1
150	-	170	200	150
T15	ASP23	ASP30	ASP60	
180	110	125	160	

		TABLE 2	6	
M2	M2HC	M3	M4	M35
100	100	110	125	120
M42	REX 20	REX 25	REX 76	T1
120	120	130	130	100
T15	ASP23	ASP30	ASP60	
130	110	120	135	

		TABLE :	3	
M2	M2HC	M3	M4	M35
100	100	110	115	110
M42	REX 20	REX 25	REX 76	T1
125	125	125	125	100
T15	ASP23	ASP30	ASP60	
125	110	110	135	

M2	M2HC	M3	M4	M35
100	100	100	100	120
M42	REX 20	REX 25	REX 76	T1
125	125	140	200	100
T15	ASP23	ASP30	ASP60	
200	100	120	160	

As pointed out earlier, there is a definite trade-off between wear resistance/red hardness (flank wear and cratering) vs. toughness (chipping and flank wear). It is due to this tradeoff that in most instances, the cutting conditions will change in relation to the tool material being used.

Table 2 lists some relative extended life values for different tool steels as they are related to an M2 tool. Example: You can expect an estimated 25% more parts per tool if you compare M4 to M2.

In the tool cost section it was stated that approximately 85% of the total manufacturing cost is due to machining cost. This machining cost is directly related to feeds and speeds in any given application. To effectively decrease machining cost, it is required that the volume of stock removal per unit

(continued on page 47)

CLASSIFIED

Rates: Classified Display—\$100 per inch (minimum 3") Type will be set to advertiser's layout or *Gear Technology* will set type at no extra charge. Word Count: 35 characters per line, 7 lines per inch.

HELP WANTED

GEAR MANUFACTURING ENGINEER

We are an established Mid-Atlantic state gear and power transmission manufacturer.

If you have solid experience in large helical gear cutting and gear grinding and are interested in better opportunities, we would like to talk with you.

We have a variety of gear tooth grinding machines and are looking for an engineer with technical knowledge of gear processing and quality requirements up to AGMA 10-15 gearing. Should have knowledge of set-up and tooling required for gear cutting and grinding operations.

The salary we offer is in keeping with your ability and the responsibilities of the job. In addition, we have liberal benefits in terms of health and welfare, dental, vacation, holiday and pension plan.

If you are interested in a challenging career working with experts in the industry, send us a letter/resume to:

F.D., P.O. Box 2059 Philadelphia, PA 19103

Equal Opportunity Employer, M/F

Machine Shop Foreman. Foreman of all machine shop operations, including all grinding such as bevel gear external and internal super-vise lathe and milling operations; responsible for numerical control; and quality control of all items produced in the machine shop operations; supervise training of apprentices and new employees in machine shop. Must have three years experience in the offered position of four years experience as setter or trainer in gear grinding department and one year training as craft apprentice or on-the-job training in machining skills. No formal education required. Applicants will be examined in regard to experience in training apprentices and new employees in machining and grinding operations. 40 hours per week plus 8 hours of overtime. 6:55 A.M. to 3:25 P.M. \$14.61 per hour. Overtime paid at the rate of \$21.92 per hour. Send resume to: Illinois Job Service, 910 South Michigan Avenue, Room 333, Chicago, Illinois 60605. Reference No. 4928-J. Attn: M. Jaskowiak. An employer paid ad.

Payment: Full payment must accompany classified ads. Mail copy to Gear Technology, P.O. Box 1426, Elk Grove Village, IL 60007. Agency Commission: No agency commission on classifieds. Closing date: Ads must be received by the 25th of the month, two months prior to publication. Acceptance: Publisher reserves the right to accept or reject classified advertisements at his discretion.

SUBCONTRACT WORK

HOBBER REBUILDING SPECIALISTS

Having trouble meeting today's demand quality control tolerances? Let our factory trained and experienced staff return your machine to optimum operating condition.

We specialize in repairing, rebuilding and modernizing all makes of hobbers.

- Cleveland Rigidhobbers
- Gould & Eberhardt
- Barber Colman

PRESSMATION INC.

522 Cottage Grove Road Bloomfield, Conn. 06002 (203) 242-8525

CIRCLE A-22 ON READER REPLY CARD





B&R MACHINING

PO Box 536 Sharon, TN 38255 1-800-238-0651

CIRCLE A-21 ON READER REPLY CARD

HELP WANTED

Engineer

MECHANICAL/ ELECTRO-MECHANICAL ENGINEER

MPC is a leading design/manufacturer of precision electro-mechanical components and assemblies for the aircraft and aerospace industries. Our growth has created an opening for a degreed engineer with experience in the design of gears, small mechanisms, actuators or flight controls. The position will include design and development of actuators, client interaction, and internal coordination. We offer challenge, responsibility and an excellent salary/benefit package. Please submit your resume including current salary to:

Personnel

MPC PRODUCTS CORP. 7426 N. Linder Skokie, IL 60077

an equal opportunity employer m/f


PURDY IS "GEARED UP"

THE PURDY CORPORATION IS NOW ABLE TO ACCOMMODATE YOUR GROUND BEVEL GEAR AND GLEASON RSR CUTTER NEEDS.

OUR STATE OF THE ART MANU-FACTURING CENTER CAN HANDLE ANY PHASE OF GEAR PRODUC-TION.

FOR FURTHER INFORMATION AND PLANT INSPECTION: CALL OR WRITE:

THE PURDY CORPORATION 586 HILLIARD ST. MANCHESTER, CT 06040 TEL. (203) 649-0000

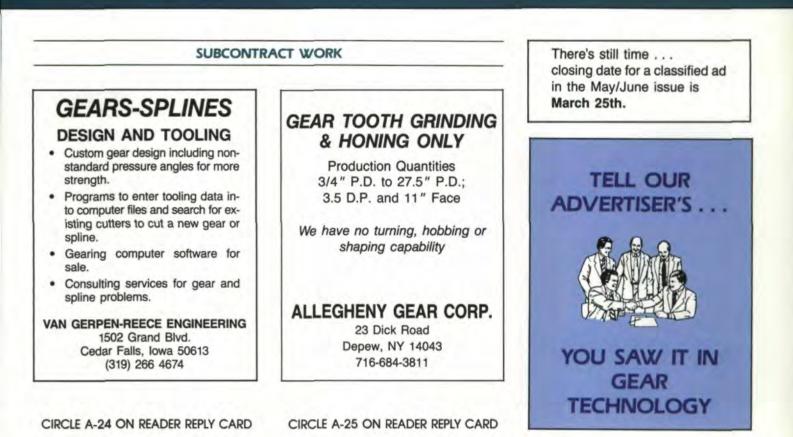

DESIGN AND SELECTION OF HOBS . . . (continued from page 45)

time be increased by increasing the feed and/or speed. Maximum values in this area are sought with regard to:

- a. Tolerances specified.
- b. Surface finished required.
- c. Stability and design of machine.

Some typical figures for relative feeds and speeds are shown in Table 3 and 4. As with the other comparison tables, all the materials are shown in relation to an M2 tool. It should be pointed out that these figures are only approximations. Actual results may vary according to how aggressively the original M2 tool is being applied.

Titanium Nitride Coatings

To develop the proper tool design for a specific application, yet another variable must be given consideration - titanium nitride coatings.

In an effort to improve tool life and increase the productivity of the gear cutting process, extensive research and development has taken place in the past few years to successfully apply titanium nitride coatings to high speed steel tools. The intent of this section is to suggest the importance of proper selection of high speed steels used in combination with titanium nitride coatings.

There are two modes of failure directly related to the substrate material used with titanium nitride coated tools, cratering, and lack of adherence.

After a coated tool (hob, shaper cutter) is sharpened, the titanium nitride layer is removed from the cutting face of the tooth. This exposes the substrate material and thus, the cratering resistance is only as good as the base metal. If the primary mode of failure on an uncoated tool is cratering, simply coating the tool with titanium nitride is not the solution. Another point to keep in mind is that although cratering was not a problem with the uncoated tool, with increased feeds and speeds and more pieces per sharpening being cut, it is likely that cratering may become a problem. Whether cratering was a problem with the uncoated tool or developed after titanium nitride coating, it would be suggested to try a higher alloy steel (one high in abrasion resistance). If cratering continues to be a problem after trying different tool steels, it may be necessary to revise (slow down) the operating conditions.

Occasionally, the wear pattern of coated cutting tools can be flaking close to the cutting edge. Consequently, the tool

(continued on page 48)